

DRAFT UGANDA STANDARD

First Edition
2019-mm-dd

Fishing gill nets — Specification

PUBLIC REVIEW DRAFT

Reference number
DUS DEAS 970: 2019

Compliance with this standard does not, of itself confer immunity from legal obligations

A Uganda Standard does not purport to include all necessary provisions of a contract. Users are responsible for its correct application

© UNBS 2019

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilised in any form or by any means, electronic or mechanical, including photocopying and microfilm, without prior written permission from UNBS.

Requests for permission to reproduce this document should be addressed to

The Executive Director
Uganda National Bureau of Standards
P.O. Box 6329
Kampala
Uganda
Tel: +256 417 333 250/1/2
Fax: +256 414 286 123
E-mail: info@unbs.go.ug
Web: www.unbs.go.ug

National foreword

Uganda National Bureau of Standards (UNBS) is a parastatal under the Ministry of Trade, Industry and Cooperatives established under Cap 327, of the Laws of Uganda, as amended. UNBS is mandated to co-ordinate the elaboration of standards and is

- (a) a member of International Organisation for Standardisation (ISO) and
- (b) a contact point for the WHO/FAO Codex Alimentarius Commission on Food Standards, and
- (c) the National Enquiry Point on TBT Agreement of the World Trade Organisation (WTO).

The work of preparing Uganda Standards is carried out through Technical Committees. A Technical Committee is established to deliberate on standards in a given field or area and consists of representatives of consumers, traders, academicians, manufacturers, government and other stakeholders.

Draft Uganda Standards adopted by the Technical Committee are widely circulated to stakeholders and the general public for comments. The committee reviews the comments before recommending the draft standards for approval and declaration as Uganda Standards by the National Standards Council.

This Draft Uganda Standard, DUS DEAS 970: 2019, *Fishing gill nets — Specification*, is identical with and has been reproduced from an International Standard, DEAS 970: 2019, *Fishing gill nets — Specification*, and is being proposed for adoption as a Uganda Standard.

The committee responsible for this document is Technical Committee UNBS/TC 7, *Textiles, leather, paper and related products*, Subcommittee SC 1, *Textiles and related products*.

Wherever the words, "East African Standard " appear, they should be replaced by "Uganda Standard."



DRAFT EAST AFRICAN STANDARD

Fishing gill nets — Specification

EAST AFRICAN COMMUNITY

Copyright notice

This EAC document is copyright-protected by EAC. While the reproduction of this document by participants in the EAC standards development process is permitted without prior permission from EAC, neither this document nor any extract from it may be reproduced, stored or transmitted in any form for any other purpose without prior written permission from EAC.

Requests for permission to reproduce this document for the purpose of selling it should be addressed as shown below or to EAC's member body in the country of the requester:

© East African Community 2018 — All rights reserved
East African Community
P.O. Box 1096,
Arusha
Tanzania
Tel: + 255 27 2162100
Fax: + 255 27 2162190
E-mail: eac@eachq.org
Web: www.eac-quality.net

Reproduction for sales purposes may be subject to royalty payments or a licensing agreement. Violators may be prosecuted.

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Requirements	2
4.1 Twines	2
4.2 Dimensional stability of mesh	2
4.3 Mesh size	2
4.4 Length and depth	2
4.5 Linear density	2
4.6 Breaking strength of twine	2
4.7 Elongation at break	2
4.8 Mesh breaking load	3
5 Packaging	4
6 Labelling	4
Annex A (normative) Measurement of mesh size	5
A.1 Principle	5
A.2 Apparatus	5
A.3 Preparation	5
A.4 Procedure	5
A.5 Calculation and expression of results	5
Annex B (normative) Determination of Linear density of twines	7
B.1 Principle	7
B.2 Apparatus	7
B.3 Preparation	7
B.4 Procedure	7
B.5 Calculation and expression of results	7
Annex C (normative) Determination of breaking strength of twine	8
C.1 Principle	8
C.2 Preparation	8
C.3 Procedure	8
C.4 Calculation and expression of results	8
Bibliography	Error! Bookmark not defined.

Foreword

Development of the East African Standards has been necessitated by the need for harmonizing requirements governing quality of products and services in the East African Community. It is envisaged that through harmonized standardization, trade barriers that are encountered when goods and services are exchanged within the Community will be removed.

The Community has established an East African Standards Committee (EASC) mandated to develop and issue East African Standards (EAS). The Committee is composed of representatives of the National Standards Bodies in Partner States, together with the representatives from the public and private sector organizations in the community.

East African Standards are developed through Technical Committees that are representative of key stakeholders including government, academia, consumer groups, private sector and other interested parties. Draft East African Standards are circulated to stakeholders through the National Standards Bodies in the Partner States. The comments received are discussed and incorporated before finalization of standards, in accordance with the Principles and procedures for development of East African Standards.

East African Standards are subject to review, to keep pace with technological advances. Users of the East African Standards are therefore expected to ensure that they always have the latest versions of the standards they are implementing.

The committee responsible for this document is Technical Committee EASC/TC 061, Textile, Textile products and Accessories

Fishing gill nets — Specification

1 Scope

This Draft East African Standard specifies the requirements and methods of test for fishing gill nets.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1805, *Fishing nets — Determination of breaking force and knot breaking force of netting yarns*

ISO 1973, *Textile fibres — Determination of linear density — Gravimetric method and vibroscope method*

ISO 5079, *Textile fibres — Determination of breaking force and elongation at break of individual fibres*

ISO 16373-1, *Textiles — Dyestuffs — Part 1: General principles of testing coloured textiles for dyestuff identification*

ISO 16373-2, *Textiles — Dyestuffs — Part 2: General method for the determination of extractable dyestuffs including allergenic and carcinogenic dyestuffs (method using pyridine-water)*

ISO 16373-3, *Textiles — Dyestuffs — Part 3: Method for determination of certain carcinogenic dyestuffs (method using triethylamine/methanol)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

— ISO Online browsing platform: available at <http://www.iso.org/obp>

3.1

half mesh

distance from the centre of one knot to the centre of the next knot in the square mesh

3.2

full mesh

distance from the centre of one knot to the next in the diagonally stretched mesh state

3.3

knot

point of connecting, overlapping or crossing of the net

3.4

twine

product of one twisting operation embracing two or more single yarns

3.5

mesh size

size of spacing between the individual strands of a fishing net or other mesh

3.6

competent authority

ministry in charge of fisheries

4 Requirements

4.1 Twines

The twines used in the manufacture of fishing nets shall be made of synthetic multifilament fibres.

4.2 Dimensional stability of mesh

The twine used in the manufacture of fishing nets shall not shrink or stretch by more than 3 % after immersion in saline water for 24 h at room temperature.

4.3 Mesh size

Mesh size for fishing nets shall comply with the requirements of the relevant legislation in Partner States.

The mesh size shall be determined in accordance with Annex A.

4.4 Length and depth

The length of the net when stretched shall be 90 m (100 yards) subject to a tolerance of 2 % variation and the shall be determined by the competent authority

4.5 Linear density

The linear density of the twine shall be as declared subject to a tolerance of 5 % when determined in accordance with ISO 1973.

4.6 Breaking strength of twine

The average breaking load of twine shall be as specified in Table 1 when determined in accordance with Annex C. Each individual test value shall be at least 90 % of the minimum breaking strength given in Table 1.

4.7 Elongation at break

The average elongation at break of the twine shall be as specified in Table 1 when determined in accordance with ISO 5079. No individual test value shall be more than 10 % of the maximum given in Table 1

Table 1 — Breaking load of twine and elongation at break

Twine construction	Breaking load, wet*, min N	Elongation at break, wet*, max. %	Test method
--------------------	-------------------------------	--------------------------------------	-------------

Nylon multifilament twine tex/plies:			
• 23/2	25	30	
• 23/6	75	35	
• 23/9	100	40	
• 23/21	240	40	ISO 5079
Polyethylene:			
• 42/6	115.0	40	
• 42/9	155.0	45	
• 42/12	196.0	50	
• 42/24	325	55	ISO 5079
<p>* "Wet" shall mean that the test specimen has been immersed in seawater without wetting agents at 25 °C ± 2 °C for at least 12 h surplus water shall be shaken off.</p> <p>NOTE 1 kgf = 9.80 N</p>			

4.8 Mesh breaking load

The average mesh breaking load of the net shall be as given in Table 2 when determined in accordance with ISO 1805.

Table 2 — Mesh breaking load

Net construction	Mesh breaking load, wet*, min. N	Test method
Nylon multifilament nets [Tex x mesh size (mm)]		
• 23/2 x 45	30	
• 23/6 x 65	80	
• 23/6 x 121	90	
• 23/6 x 127	110	
• 23/9 x 76	110	
• 23/21 x 102	290	ISO 1805
Polyethylene nets [Tex/plies x size (mm)]		
• 42/6 x 32	90	
• 42/6 x 45	100	
• 42/9 x 45	140	
• 42/12 x 45	120	
• 42/24 x 152	350	ISO 1805
<p>* "Wet" shall mean that the test specimen has been immersed in seawater without wetting agents at 25 °C ± 2 °C for at least 12 h surplus water shall be shaken off.</p>		

5 Restricted Colorants

The dyed fishing nets shall be free from listed amines and carcinogenic dyestuffs specified in ISO 16373, 2 & 3. Dyestuff classes are identified in accordance with ISO 16373-1

6. Packaging

Fishing nets shall be packed in suitable packages so as to prevent soiling and damage.

7 Labelling

The following information shall be legibly and indelibly marked on the fishing gill nets:

- a) name of the product shall be "Fishing gill nets";
- b) manufacturers name or registered trade mark;
- c) twine specification;
- d) fibre content of the net twine;
- e) nominal mesh size;
- f) length of the net
- g) depth of the net;
- h) colour of the net;
- i) date of manufacture;
- j) instructions for care and disposal of nets as per country regulation; and
- k) country of manufacture

Annex A

(normative)

Measurement of mesh size

A.1 Principle

The distance from knot to knot in a square mesh configuration or stretched mesh configuration shall be taken to give the size of half mesh or full mesh respectively.

A.2 Apparatus

One of the following measuring devices shall be used to measure mesh size:

- a) allen net rule;
- b) hovey gauge;
- c) selkirk gauge;
- d) flexible rule; or
- e) straight rule.

A.3 Preparation

Immerse the fishing net sample in seawater without wetting agents at $25\text{ }^{\circ}\text{C} \pm 2\text{ }^{\circ}\text{C}$ for at least 12 h. Shake off surplus water.

A.4 Procedure

A.4.1 Take the distance in millimetres, from the centre of one knot to the next in the square mesh condition. Repeat the measurement for 11 other meshes selected at random.

A.4.2 Measure the distance in millimetres from the centre of one knot to the next in the stretched mesh state using just sufficient force to remove kinks. Repeat the measurement for 11 other meshes selected at random.

NOTE See Figure A.1.

A.5 Calculation and expression of results

A.5.1 Full mesh size is the average of the measurements in A.4.2.

A.5.2 Half mesh size is the average of measurements taken in A.4.1.

Full mesh size = Half mesh size times 2.

NOTE See Figure A.1.

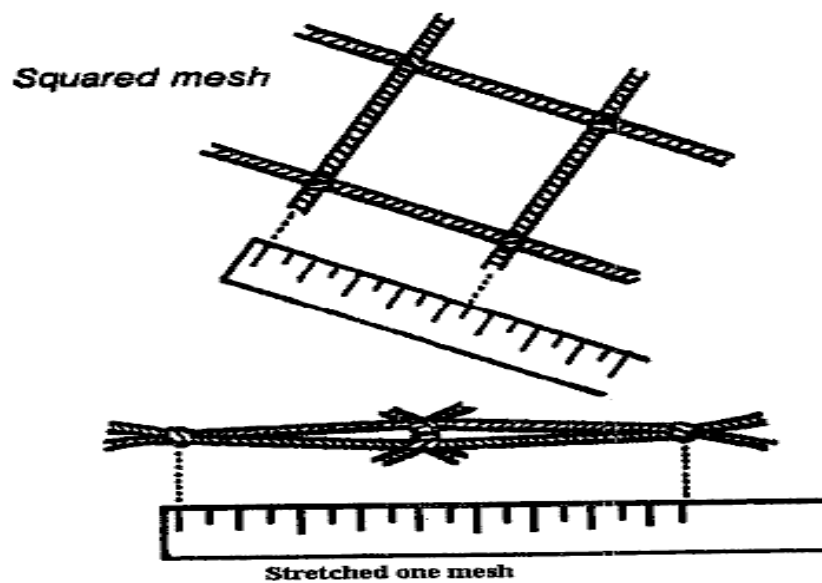


Figure A.1 — Mesh size

Annex B

(normative)

Determination of Linear density of twines

B.1 Principle

Certain length of twine shall be weighed in milligrams and its length in centimetres determined. Its linear density shall be calculated from the two measurements.

B.2 Apparatus

B.2.1 Weighing balance, capable of measuring in milligrams

B.2.2 Apparatus in A.2 above

B.3 Preparation

Unravel 10 pieces of twine from the netting each measuring at least 15 cm. Apply just sufficient force to remove kinks in the twine pieces.

B.4 Procedure

B.4.1 Measure the length of each piece in centimetres to the nearest millimetre.

B.4.2 Measure the mass of each twine piece to the nearest milligram.

B.5 Calculation and expression of results

B.5.1 Linear density of each twine piece in tex shall be calculated from the following formula:

$$\text{Tex} = 100 \, m/l$$

where

l is the length, in centimetres, of the piece; and

m is the mass, in milligrams, of the piece.

B.5.2 Linear density of the netting twine = the average tex of the 10 pieces

Annex C

(normative)

Determination of breaking strength of twine

C.1 Principle

A piece of twine is subjected to tensile loading until it breaks. The load at which it breaks shall be noted and recorded as breaking strength.

C.2 Preparation

Retrieve the twine pieces used in Annex B for this test.

C.3 Procedure

Determine the breaking strength of each piece using ISO 5079 but using gauge length of 10 cm.

C.4 Calculation and expression of results

C.4.1 Take the average breaking strength of the 10 twine pieces.

C.4.2 The breaking strength of the netting twine shall be the average in C.4.1.

DRAFT UNDER PUBLIC REVIEW